

Asymmetric Free-Space Light Transport at Nonlinear MetasurfacesNir Shitrit,¹ Jeongmin Kim,¹ David S. Barth,¹ Hamidreza Ramezani,^{1,2} Yuan Wang,¹ and Xiang Zhang^{1,3,*}¹*NSF Nanoscale Science and Engineering Center (NSEC), 3112 Etcheverry Hall, University of California, Berkeley, California 94720, USA*²*Department of Physics and Astronomy, University of Texas Rio Grande Valley, Brownsville, Texas 78520, USA*³*Materials Sciences Division, Lawrence Berkeley National Laboratory, 1 Cyclotron Road, Berkeley, California 94720, USA*

(Received 12 March 2018; published 24 July 2018)

Asymmetric light transport has significantly contributed to fundamental science and revolutionized advanced technology in various aspects such as unidirectional photonic devices, optical diodes, and isolators. While metasurfaces mold wave fronts at will with an ultrathin flat optical element, asymmetric transport of light cannot be fundamentally achieved by any linear system including linear metasurfaces. We report asymmetric transport of free-space light at nonlinear metasurfaces upon transmission and reflection. Moreover, we theoretically derive the nonlinear generalized Snell's laws that were experimentally confirmed by the anomalous nonlinear refraction and reflection. The asymmetric transport at optically thin nonlinear interfaces is revealed by the concept of a reversed propagation path. Such an asymmetric transport at metasurfaces opens a new paradigm for free-space ultrathin lightweight optical devices with one-way operation including unrivaled optical valves and diodes.

DOI: [10.1103/PhysRevLett.121.046101](https://doi.org/10.1103/PhysRevLett.121.046101)

Wave propagation, from sound to light, is generally two-way symmetric; i.e., forward and backward paths are identical. Nevertheless, the quest for protecting a laser from back reflections or improving information capacity in optical communication technology by mitigating a multi-path interference calls for asymmetric transport (AT). AT is an uneven physical response of counterpropagating signals that has contributed to fundamental science and revolutionized advanced technology via a variety of significant devices including circulators and isolators (diodes) in electronics [1], optics [2–5], acoustics [6], and heat transfer [7]. While photonic metasurfaces have facilitated applications of free-space optics with an ultracompact lightweight advantage, such an architecture can be potentially harnessed to achieve asymmetric free-space transport of light. Photonic gradient metasurfaces are two-dimensional ultrathin arrays of engineered meta-atoms (nanoscatterers) that mold optical wave fronts at the subwavelength scale by imparting rapid phase changes along an interface [8–11]. These subwavelength-structured interfaces enable a custom-tailored electromagnetic response with unprecedented control over the fundamental properties of light, i.e., phase, amplitude, and polarization. Gradient metasurfaces aim to revolutionize optical designs by realizing virtually flat, ultrathin, and lightweight optics [10,11] that replaces bulky optical elements. Free-space wave front molding at will by gradient metasurfaces encompasses abnormal light bending [12,13], planar lenses [14,15], optical vortex generators [12,13], and photonic multitasking [16], etc. However, excluding time dependence and magnetic response, AT of

light cannot be fundamentally achieved by any linear system [5] including linear metasurfaces.

Nonlinear processes or nonlinear materials can be employed to achieve AT [5]. Hence, the emerging nonlinear metasurfaces [17–19] may leverage AT. By combining nonlinear harmonic generation at interfaces and spatially varying effective nonlinear polarizability with a controllable phase [17,18], nonlinear gradient metasurfaces (NGMs) offer nonlinear wave front shaping [19,20]. The milestones of achieving extraordinary efficiency of nonlinear generation at a subwavelength thickness [21–24] and continuous control of the nonlinear phase [18,22] have opened a new paradigm of flat nonlinear optics. Previous demonstrations of AT aimed at on-chip (waveguide) architectures [1–4] or required propagation through an inherently bulky configuration of a superlattice coupled to a nonlinear medium [6]. However, the highly desirable asymmetric free-space transport of light at an optically thin flatland, in both transmission and reflection, has not yet been demonstrated. Here, we report the experimental observation of asymmetric free-space transport of light at NGMs upon transmission and reflection. We also derive the generalized laws of refraction and reflection for NGMs, which were experimentally verified by angle-resolved anomalous refraction and reflection of the nonlinear light. Asymmetric free-space transport with metasurfaces provides a route to ultrathin lightweight optical platforms with unidirectional operation including ultrathin optical valves and diodes.

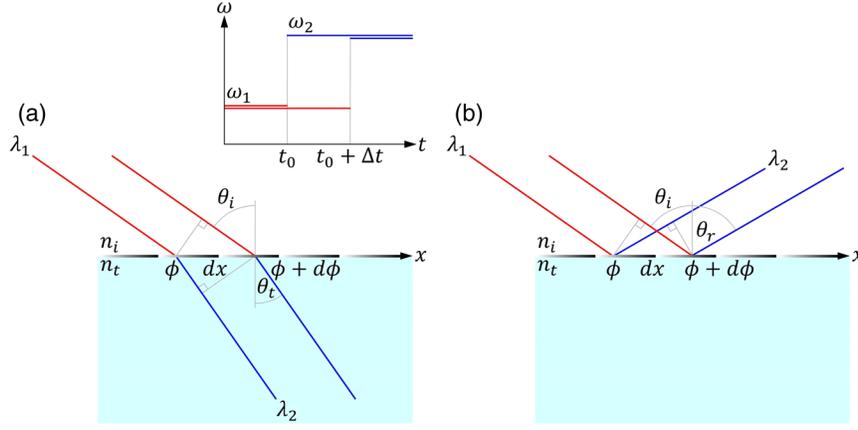


FIG. 1. Generalized laws of refraction and reflection at nonlinear gradient metasurfaces. (a),(b) Schematics used to derive the generalized laws of refraction and reflection for NGMs, respectively, wherein the optical path differences and the rapid phase shift (grayscale pattern) introduced by the metasurface are depicted. Red and blue rays correspond to rays of light at the fundamental wavelength λ_1 and at the wavelength of the generated nonlinear harmonic λ_2 , respectively. ϕ and $\phi + d\phi$ are the phase shifts at the two locations in which the rays cross the interface. The inset in (a) illustrates the temporal phase delay originating from the time difference Δt in the generation of the nonlinear harmonic between the two crossing locations. The three factors of optical path differences, spatial-temporal nonlinear phase delay, and metasurface-induced phase shift give rise to the nonlinear generalized Snell's laws of refraction $n_t(\lambda_2) \sin \theta_r - n_i(\lambda_1) \sin \theta_i = (\lambda_1/2\pi n)(d\phi/dx)$ and reflection $n_i(\lambda_2) \sin \theta_r - n_i(\lambda_1) \sin \theta_i = (\lambda_1/2\pi n)(d\phi/dx)$, where n is the order of the generated nonlinear harmonic.

We consider a NGM as an optical interface between two media with an inherent rapid phase shift, wherein a nonlinear harmonic is generated (Fig. 1). Harmonic generation in NGMs requires revisiting the generalized Snell's laws of refraction and reflection originally introduced for linear gradient metasurfaces [13]. We consider an incident plane wave at an angle θ_i at the fundamental harmonic (FH) and two light rays which are infinitesimally close to the actual light path (Fig. 1). In its general form known as the principle of stationary phase [25], Fermat's principle states that the variation of the phase accumulated along the actual light path is zero with respect to infinitesimal variations of the path. Accordingly, Fermat's principle corresponding to refraction at NGMs is formulated as

$$\left(\frac{\omega_1}{c} n_i(\omega_1) \sin \theta_i dx - \frac{\omega_2}{c} n_t(\omega_2) \sin \theta_t dx \right) + (\omega_2 - \omega_1) \Delta t + d\phi = 0. \quad (1)$$

Here, ω_1 is the fundamental frequency, whereas $\omega_2 = n\omega_1$ is the frequency of the generated nonlinear harmonic of order n ; c is the speed of light in a vacuum; $n_i(\omega_1)$ and $n_t(\omega_2)$ are the refractive indices of the two media at the fundamental and nonlinear harmonic generation frequencies, respectively; θ_i is the angle of refraction, dx is the infinitesimal distance between the locations in which the two light rays cross the interface, and $d\phi$ is the phase difference between these two locations associated with the metasurface. While the first term is the optical path differences [Fig. 1(a)], the second expression is attributed to the time-harmonic dependence of electromagnetic fields. As the two light rays meet the

interface at a time delay of $\Delta t = \sin \theta_i dx / [c/n_i(\omega_1)]$, the nonlinear harmonic is locally generated at different times along the NGM, giving rise to a temporal phase delay of $(\omega_2 - \omega_1) \Delta t$ [see Fig. 1(a), inset]. Note that, in stark contrast to linear gradient metasurfaces (i.e., $\omega_2 = \omega_1$), this term solely emerges in NGMs. By considering a constant phase gradient, we obtained the generalized Snell's law of refraction for NGMs

$$n_t(\lambda_2) \sin \theta_t - n_i(\lambda_1) \sin \theta_i = \frac{\lambda_1}{2\pi n} \frac{d\phi}{dx}, \quad (2)$$

where $\lambda_1 = 2\pi c/\omega_1$ and $\lambda_2 = \lambda_1/n$ are the free-space wavelengths associated with the FH and the nonlinear harmonic generation, respectively.

Similarly, the generalized law of reflection corresponding to NGMs is

$$n_i(\lambda_2) \sin \theta_r - n_i(\lambda_1) \sin \theta_i = \frac{\lambda_1}{2\pi n} \frac{d\phi}{dx}, \quad (3)$$

where θ_r is the angle of reflection [Fig. 1(b)]. By introducing the anomalous refraction and reflection of the beams associated with the FH and nonlinear harmonic generation, these generalized laws of refraction and reflection govern the molding of optical wave fronts via custom-designed structured interfaces that mimic phase gradients. Note that this concept is unified, as for the fundamental wave (i.e., $n = 1$) the derived laws coincide with the generalized Snell's laws referring to linear gradient metasurfaces [13]. Beyond the scope of metasurfaces, these nonlinear generalized Snell's laws play a role of a working tool in nonlinear optics.

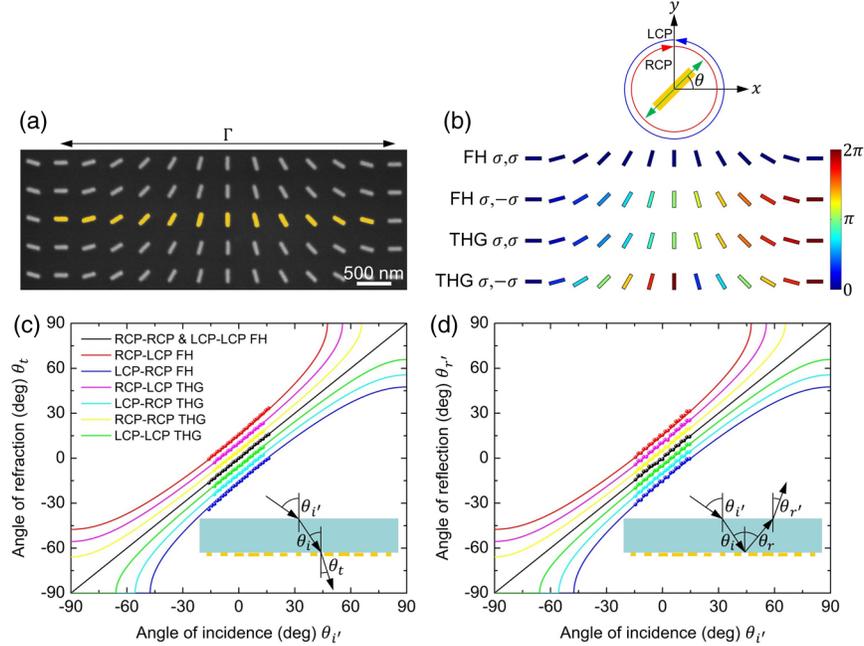


FIG. 2. Anomalous refraction and reflection from nonlinear gradient metasurfaces. (a) Scanning electron microscope image of the NGMs. The unit cell of the NGMs (yellow) comprises 12 gold nanorod antennas, where their orientation angles $\theta(x, y)$ rotate linearly to generate a constant phase gradient. The width and length of each nanorod are 50 and 240 nm, respectively, and the thickness is 30 nm. The unit cell repeats with a periodicity Γ of $4.8 \mu\text{m}$ along the x direction and 400 nm along the y direction. The gold metasurface was coated with a 100-nm-thick PFO layer to form metal-organic hybrid nonlinear metasurfaces. (b) The same metasurface structure introduces different phase distributions for the FH and THG (resembling linear and NGMs, respectively). Colors filling the nanorods depict the local phase. The FH beam experiences a constant phase for the modes maintaining the polarizations (σ, σ modes), while the modes flipping the polarizations ($\sigma, -\sigma$ modes) experience a linear phase profile from 0 to 2π . The THG beam experiences linear phase profiles from 0 to 2π and from 0 to 4π for σ, σ and $\sigma, -\sigma$ modes, respectively. The phase profiles portrayed by color correspond to right circular polarization (RCP) excitation ($\sigma = +1$); for left circular polarization (LCP) excitation ($\sigma = -1$), the trends of the phase profiles are similar but with the opposite slope. (c),(d) Angles of refraction (θ_t) and reflection (θ_r) versus the angle of incidence (θ_i), respectively. Modes are labeled with the incident-analyzed polarization state. Lines correspond to theoretical calculations performed by the generalized laws of refraction and reflection for NGMs [Eqs. (2) and (3)], whereas dots refer to measured data. Error bars (not shown) are smaller than the size of the data points. All angles were measured in free space as shown in the insets.

Efficient generation of nonlinear light in bulky nonlinear materials is obtained by fulfilling the phase-matching condition [26], which is an arduous task requiring a compensation method for the inherent phase mismatch between the interacting waves propagating in the nonlinear media. The ultrathin thickness of NGMs imposes a reduced form of surface phase matching [Eq. (1)] which is naturally satisfied via the redirection of the generated nonlinear light (i.e., the angle of refraction or reflection).

We demonstrated experimentally the generalized laws of refraction and reflection in nonlinear structured interfaces via a plasmonic antenna array of gold nanorods coated with a thin nonlinear active layer of poly(9,9-dioctylfluorene) (PFO). The combination of high field enhancement from the resonant plasmonic structures and large third-order nonlinearity of the PFO gives rise to strong third harmonic generation (THG) in the formed gold-PFO hybrid nonlinear metasurface [18,27]. We imprinted a rapid phase change in the nonlinear interface via the emerging concept of a nonlinear geometric phase [18,22]. The spin-rotation coupling

of light in NGMs induces a nonlinear geometric phase of $\phi(x, y) = (n \mp 1)\sigma\theta(x, y)$ for modes maintaining (σ, σ modes) or flipping ($\sigma, -\sigma$ modes) the polarization of the incident fundamental wave, respectively [18]; here, $\sigma = \pm 1$ is the polarization helicity (i.e., spin angular momentum of light in \hbar units, where \hbar is the reduced Planck's constant [28]) of the incident light corresponding to right and left circularly polarized light, respectively, and $\theta(x, y)$ is the space-variant orientation angle of the anisotropic optical nanoantennas. NGMs based on the geometric phase, also referred as nonlinear Pancharatnam-Berry phase optical elements (see Supplemental Material [29], Sec. 7), enable nonlinear wave front shaping via spatially varying effective nonlinear polarizability with a continuously controllable phase [18]. We realized a NGM with a constant phase gradient by locally rotating the nanorod antennas in such a way that their orientation angles vary linearly along the x direction [Fig. 2(a)]. Note that the FH modes resemble the response of linear metasurfaces, wherein the degenerated σ, σ modes exhibit ordinary refraction and reflection, whereas $\sigma, -\sigma$

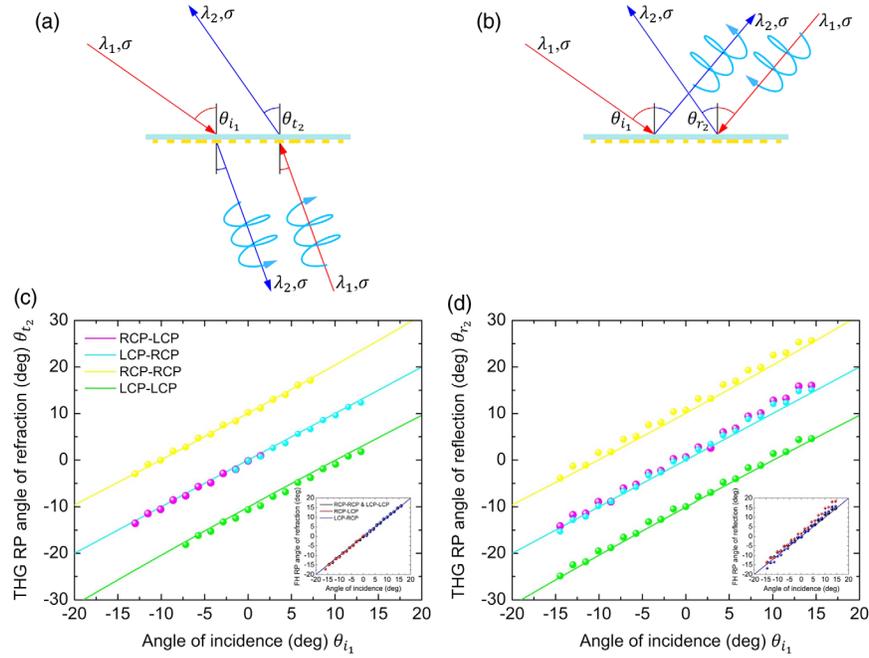


FIG. 3. Asymmetric transport at nonlinear gradient metasurfaces. (a),(b) Schematics of the concept of AT at NGMs for refraction and reflection, respectively. We first consider the angle of refraction or reflection for a given angle of incidence θ_{i_1} ; then, we excite the metasurface from the opposite side, where the angle of incidence is set to the obtained angle of refraction or reflection in the original excitation (i.e., RP path). Moreover, the handedness of the circular polarization of these two beams is identical owing to RP. The transport of light is asymmetric when the angle of refraction θ_{t_2} or reflection θ_{r_2} in the excitation from the opposite side is different from θ_{i_1} . (c),(d) THG RP angles of refraction (θ_{r_2}) and reflection (θ_{r_2}) versus the angle of incidence in the original excitation (θ_{i_1}), respectively. Lines correspond to calculations based on the generalized laws of refraction and reflection at NGMs, whereas dots refer to measured data. All angles were measured in free space. The polarization state of the modes refers to the original excitation. The insets in (c) and (d) are the corresponding results for the FH (linear metasurfaces).

modes exhibit linear anomalous refraction and reflection [Fig. 2(b)]. In stark contrast to the FH, all THG ($n = 3$) modes undergo nonlinear anomalous refraction and reflection, where $\sigma, -\sigma$ modes experience a stronger phase gradient than σ, σ modes [Fig. 2(b)]. Moreover, according to selection rules for harmonic generation [18], all polarization modes for both FH and THG signals are allowed with the twofold rotational symmetry of the nanorod, enabling versatile linear and nonlinear wave front shaping with the same structure.

We pumped the metasurface by a femtosecond laser at the wavelength of $1.26 \mu\text{m}$ (i.e., the localized plasmon resonance of the hybrid metasurface; see Supplemental Material [29], Sec. 2) and imaged the k space of the scattered light while varying the incident angle of the pump laser; by controlling the incident polarization, probing the desired polarization of the scattered light, and filtering out the wavelength of the pump laser via a bandpass filter, all FH and THG (at the wavelength of 420 nm) modes were measured (see Supplemental Material [29], Sec. 4 for the experimental setup). The angles of refraction and reflection, extracted from the k -space imaging, as a function of the angle of incidence [Figs. 2(c) and 2(d), respectively] exhibit good agreement with theoretical calculations performed by the generalized laws of refraction

for NGMs [Eqs. (2) and (3)]. Note that, in transmission measurements, light incident from the substrate side is anomalously refracted to air by the metasurface interface [see Fig. 2(c), inset]; in reflection measurements, light incident from the substrate side is anomalously reflected to the substrate by the metasurface and then ordinarily refracted to air [see Fig. 2(d), inset]. In different ranges of the angle of incidence, FH and THG modes reveal “negative” refraction and reflection [Figs. 2(c) and 2(d)]. The polarization-dependent critical angles for total internal reflection [Fig. 2(c)] and critical angles of incidence above which the reflected beam becomes evanescent [Fig. 2(d)] are evident for the FH and THG (see Supplemental Material [29], Sec. 3 for the detailed analysis).

By offering new functionalities that cannot be achieved with linear metasurfaces, NGMs take the molding of optical wave fronts to a new level. We specifically aimed at AT of light in ultrathin structured interfaces. Note that AT was theoretically proposed in time-varying metasurfaces [30,31], i.e., interfaces wherein a temporal gradient is added to the conventional spatial gradient, which have not yet been realized. In the context of metasurfaces, for a given angle of incidence, we consider the angle of refraction in two consecutive scenarios that are linked by

reversed propagation (RP); i.e., the angle of incidence in the bottom-to-top excitation scheme (light incident onto the metasurface from free space) is equal to the angle of refraction in the original top-to-bottom excitation (light incident onto the metasurface from the substrate) [see Fig. 3(a)]. The transport is referred as symmetric when the trajectory of light is reciprocal; i.e., the angle of refraction in the bottom-to-top excitation θ_{t_2} is equal to the angle of incidence in the primary top-to-bottom excitation θ_{i_1} [see Fig. 3(a)]. Otherwise (i.e., $\theta_{t_2} \neq \theta_{i_1}$), the transport is asymmetric. As the test for AT requires built-in polarization filters, the handedness of the circularly polarized beam launched from bottom to top is identical to the handedness of the circular polarization of the refracted beam in the top-to-bottom excitation [see Fig. 3(a)]; in a similar fashion, the polarization of the refracted beam in the bottom-to-top excitation is identical to the original polarization launched from top to bottom. This polarization requirement originates from the conservation of the helicity under time reversal while reversing the direction of propagation. Similarly, the concept of AT in metasurfaces is introduced in reflection [Fig. 3(b)].

By measuring the angle-resolved refraction and reflection angles at both top-to-bottom [Figs. 2(c) and 2(d), respectively] and bottom-to-top (Supplemental Material [29], Fig. S6) excitation schemes and mapping the corresponding polarization modes, we characterized the transport of light in metasurfaces. We revealed that NGMs exhibit AT upon refraction and reflection for the σ, σ modes, while the $\sigma, -\sigma$ modes exhibit symmetric transport [Figs. 3(c) and 3(d)]. In stark contrast, linear gradient metasurfaces show symmetric transport regardless of the polarization of the modes [Figs. 3(c) and 3(d), insets]. These observations are in good agreement with calculations based on the aforementioned generalized laws of refraction and reflection for NGMs. All-angle AT of free-space optical beams is a peculiar property of NGMs arising from the nonzero phase gradient imparted to the modes of the generated nonlinear harmonic that maintain the polarization state. The concept of AT in NGMs applies to any harmonic order; yet, we chose to demonstrate THG to avoid arduous tasks in experiments as the degree of asymmetry increases with the generated harmonic order (see Supplemental Material [29], Sec. 6). Note that at both top-to-bottom and bottom-to-top excitations the incident wavelength is the fundamental wavelength; yet, the observed AT at NGMs is not optical isolation [5], as the nonlinear metasurface enables the conversion from the FH to the generated harmonic but not vice versa.

In summary, asymmetric free-space transport of light at an optically thin flatland is reported. Note that nonlinear anomalous refraction [17,18,20] or reflection [22–24] was previously observed only at normal incidence, wherein the spatial-temporal nonlinear phase delay vanishes; therefore, we probed its contribution to the nonlinear generalized

Snell's laws by angle-dependent measurements. Moreover, the nonlinear generalized Snell's laws were derived as a working tool to explore the new functionality of AT at NGMs. The generalized laws of refraction and reflection at nonlinear interfaces apply to the entire optical spectrum for suitable designer interfaces and may introduce new degrees of freedom in nonlinear optics for designing perfect phase matching. This study may also inspire the merging of metasurface principles and nonreciprocity, where a one-way invisibility cloak, ultrathin optical diodes, and arbitrary nonreciprocal beam steering are envisioned.

This work was supported by the Gordon and Betty Moore Foundation, the Office of Naval Research Multidisciplinary University Research Initiative program under Grant No. N00014-13-1-0678, and Samsung Electronics. We also thank the Molecular Foundry, Lawrence Berkeley National Laboratory (supported by the Office of Science, Office of Basic Energy Sciences, of the U.S. Department of Energy under Contract No. DE-AC02-05CH11231) for the technical support in nanofabrication.

N. S. and J. K. contributed equally to this work.

*Corresponding author.

xiang@berkeley.edu

- [1] N. Bender, S. Factor, J. D. Bodyfelt, H. Ramezani, D. N. Christodoulides, F. M. Ellis, and T. Kottos, Observation of Asymmetric Transport in Structures with Active Nonlinearities, *Phys. Rev. Lett.* **110**, 234101 (2013).
- [2] L. Fan, J. Wang, L. T. Varghese, H. Shen, B. Niu, Y. Xuan, A. M. Weiner, and M. Qi, An all-silicon passive optical diode, *Science* **335**, 447 (2012).
- [3] H. Lira, Z. Yu, S. Fan, and M. Lipson, Electrically Driven Nonreciprocity Induced by Interband Photonic Transition on a Silicon Chip, *Phys. Rev. Lett.* **109**, 033901 (2012).
- [4] L. Feng, Y.-L. Xu, W. S. Fegadolli, M.-H. Lu, J. E. B. Oliveira, V. R. Almeida, Y.-F. Chen, and A. Scherer, Experimental demonstration of a unidirectional reflectionless parity-time metamaterial at optical frequencies, *Nat. Mater.* **12**, 108 (2013).
- [5] D. Jalas *et al.*, What is – and what is not – an optical isolator, *Nat. Photonics* **7**, 579 (2013).
- [6] B. Liang, X. S. Guo, J. Tu, D. Zhang, and J. C. Cheng, An acoustic rectifier, *Nat. Mater.* **9**, 989 (2010).
- [7] C. W. Chang, D. Okawa, A. Majumdar, and A. Zettl, Solid-state thermal rectifier, *Science* **314**, 1121 (2006).
- [8] Z. Bomzon, V. Kleiner, and E. Hasman, Pancharatnam-Berry phase in space-variant polarization-state manipulations with subwavelength gratings, *Opt. Lett.* **26**, 1424 (2001).
- [9] Z. Bomzon, G. Biener, V. Kleiner, and E. Hasman, Space-variant Pancharatnam-Berry phase optical elements with computer-generated subwavelength gratings, *Opt. Lett.* **27**, 1141 (2002).
- [10] A. V. Kildishev, A. Boltasseva, and V. M. Shalaev, Planar photonics with metasurfaces, *Science* **339**, 1232009 (2013).

- [11] N. Yu and F. Capasso, Flat optics with designer metasurfaces, *Nat. Mater.* **13**, 139 (2014).
- [12] N. Shitrit, I. Bretner, Y. Gorodetski, V. Kleiner, and E. Hasman, Optical spin Hall effects in plasmonic chains, *Nano Lett.* **11**, 2038 (2011).
- [13] N. Yu, P. Genevet, M. A. Kats, F. Aieta, J.-P. Tetienne, F. Capasso, and Z. Gaburro, Light propagation with phase discontinuities: Generalized laws of reflection and refraction, *Science* **334**, 333 (2011).
- [14] E. Hasman, V. Kleiner, G. Biener, and A. Niv, Polarization dependent focusing lens by use of quantized Pancharatnam-Berry phase diffractive optics, *Appl. Phys. Lett.* **82**, 328 (2003).
- [15] M. Khorasaninejad, W. T. Chen, R. C. Devlin, J. Oh, A. Y. Zhu, and F. Capasso, Metalenses at visible wavelengths: Diffraction-limited focusing and subwavelength resolution imaging, *Science* **352**, 1190 (2016).
- [16] E. Maguid, I. Yulevich, D. Veksler, V. Kleiner, M. L. Brongersma, and E. Hasman, Photonic spin-controlled multifunctional shared-aperture antenna array, *Science* **352**, 1202 (2016).
- [17] N. Segal, S. Keren-Zur, N. Hendler, and T. Ellenbogen, Controlling light with metamaterial-based nonlinear photonic crystals, *Nat. Photonics* **9**, 180 (2015).
- [18] G. Li, S. Chen, N. Pholchai, B. Reineke, P. W. H. Wong, E. Y. B. Pun, K. W. Cheah, T. Zentgraf, and S. Zhang, Continuous control of the nonlinearity phase for harmonic generations, *Nat. Mater.* **14**, 607 (2015).
- [19] G. Li, S. Zhang, and T. Zentgraf, Nonlinear photonic metasurfaces, *Nat. Rev. Mater.* **2**, 17010 (2017).
- [20] S. Keren-Zur, O. Avayu, L. Michaeli, and T. Ellenbogen, Nonlinear beam shaping with plasmonic metasurfaces, *ACS Photonics* **3**, 117 (2016).
- [21] J. Lee, M. Tymchenko, C. Argyropoulos, P.-Y. Chen, F. Lu, F. Demmerle, G. Boehm, M.-C. Amann, A. Alù, and M. A. Belkin, Giant nonlinear response from plasmonic metasurfaces coupled to intersubband transitions, *Nature (London)* **511**, 65 (2014).
- [22] M. Tymchenko, J. S. Gomez-Diaz, J. Lee, N. Nookala, M. A. Belkin, and A. Alù, Gradient Nonlinear Pancharatnam-Berry Metasurfaces, *Phys. Rev. Lett.* **115**, 207403 (2015).
- [23] J. Lee, N. Nookala, J. S. Gomez-Diaz, M. Tymchenko, F. Demmerle, G. Boehm, M.-C. Amann, A. Alù, and M. A. Belkin, Ultrathin second-harmonic metasurfaces with record-high nonlinear optical response, *Adv. Opt. Mater.* **4**, 664 (2016).
- [24] N. Nookala, J. Lee, M. Tymchenko, J. S. Gomez-Diaz, F. Demmerle, G. Boehm, K. Lai, G. Shvets, M.-C. Amann, A. Alu, and M. Belkin, Ultrathin gradient nonlinear metasurface with a giant nonlinear response, *Optica* **3**, 283 (2016).
- [25] E. Hecht, *Optics* (Addison-Wesley, Reading, MA, 1997).
- [26] R. W. Boyd, *Nonlinear Optics* (Academic, New York, 2008).
- [27] S. Chen, G. Li, F. Zeuner, W. H. Wong, E. Y. B. Pun, T. Zentgraf, K. W. Cheah, and S. Zhang, Symmetry-Selective Third-Harmonic Generation from Plasmonic Metacrystals, *Phys. Rev. Lett.* **113**, 033901 (2014).
- [28] K. Y. Bliokh, F. J. Rodríguez-Fortuño, F. Nori, and A. V. Zayats, Spin-orbit interactions of light, *Nat. Photonics* **9**, 796 (2015).
- [29] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevLett.121.046101> for the sample fabrication, characterization of the plasmonic resonance of nanorods and the third harmonic generation from the PFO, optical setup for angle-resolved k -space imaging of anomalous refraction and reflection from nonlinear gradient metasurfaces, anomalous nonlinear refraction at bottom-to-top excitation, derivation of the asymmetric transport of light at nonlinear gradient metasurfaces, and representation of nonlinear Pancharatnam-Berry phase optical elements.
- [30] Y. Hadad, D. L. Sounas, and A. Alu, Space-time gradient metasurfaces, *Phys. Rev. B* **92**, 100304 (2015).
- [31] A. Shaltout, A. Kildishev, and V. Shalaev, Time-varying metasurfaces and Lorentz nonreciprocity, *Opt. Mater. Express* **5**, 2459 (2015).